

Product Specification Sheet

Concrete Sand (Fine Aggregate)


Natural fine aggregate from river deposits, washed and processed to meet ASTM C33.

Typical Applications

Ready Mix Concrete

Gradation Test — ASTM C33

Sieve Size	% Passing	Required % Passing
3/8 in.	100	100
No. 4	100	95-100
No. 8	85	80-100
No. 16	65	50-85
No. 30	45	25-60
No. 50	20	5-30
No. 100	7	0-10
No. 200	2	0-3

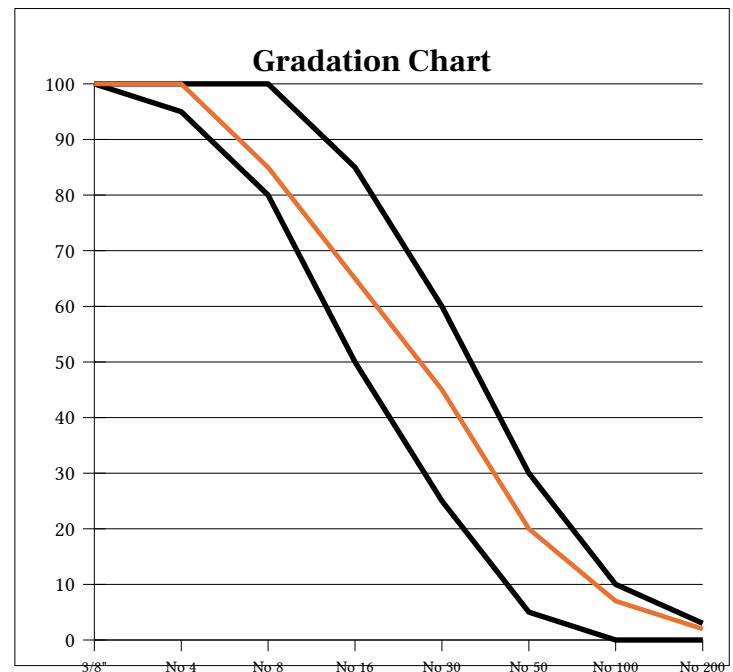

Properties	Test Value	Required Spec.
Fineness Modulus	2.78	2.3-3.1
Specific Gravity	2.57	2.55 - 2.65
Absorption	1.2	0.5% - 2.0%
Soundness	6	15% max
Sand Equivalent	88	80 min

July, 2026